arXiv:cond-mat/0312110v1 [cond-mat.mtrl-sci] 4 Dec 2003

# Magnetocaloric effect and magnetization in a Ni-Mn-Ga Heusler alloy in the vicinity of magnetostructural transition

A. Aliev,[1] A. Batdalov,[1] S. Bosko,[2] V. Buchelnikov,[2] I. Dikshtein,[3]
V. Khovailo,[4] V. Koledov,[3] R. Levitin,[5] V. Shavrov,[3] and T. Takagi[6]
[1]*Institute of Physics of Dagestan SC RAS, Makhachkala 367003, Russia*
[2]*Chelyabinsk State University, Chelyabinsk 454021, Russia*
[3]*Institute of Radioengineering and Electronics of RAS, Moscow 101999, Russia*
[4]*National Institute of Advanced Industrial Science and Technology, Tohoku Center, Sendai 983-8551, Japan*
[5]*Physics Depertment, Moscow State University, Moscow 119899, Russia*
[6]*Institute of Fluid Science, Tohoku University, Sendai 980-8577, Japan*

The magnetic and thermodynamic properties of a $\mathrm{Ni_{2.19}Mn_{0.81}Ga}$ alloy with coupled magnetic and structural (martensitic) phase transitions were studied experimentally and theoretically. The magnetocaloric effect was measured by a direct method in magnetic fields $0-26$ kOe at temperatures close to the magnetostructural transition temperature. For theoretical description of the alloy properties near the magnetostructural transition a statistical model is suggested, that takes into account the coexistence of martensite and austenite domains in the vicinity of martensite transformation point.

Keywords: Ferromagnetism; Magnetostructural phase transition; Magnetization; Magnetocaloric effect

In recent year $\mathrm{Ni_2MnGa}$-based ferromagnetic shape memory alloys have attracted considerable attention as a new class of actuator materials (see, for a recent review, Ref. [1]). Giant magnetocaloric effect (MCE) has also been observed in these alloys. Solid state materials with a large MCE are considered to be very perspective in creation of solid state refrigerators with high efficiency, manufacturability and ecological compatibility (Ref. [2] and references therein). In Ni-Mn-Ga alloys, the martensitic transition temperature is very sensitive to composition, which is very important for practical applications of these alloys. For instance, upon a partial substitution of Mn for Ni the martensitic transition temperature $T_m$ increases and Curie temperature $T_C$ decreases until they merge in one first-order magnetostructural phase transition (MSPT) [1]. The values of MCE in the vicinity of such a transition are likely to be maximal. The aim of our work has been to study, experimentally and theoretically, magnetic and thermodynamic properties of $\mathrm{Ni_{2.19}Mn_{0.81}Ga}$ alloy with MSPT and to determine directly the magnitude of MCE.

Polycrystalline $\mathrm{Ni_{2.19}Mn_{0.81}Ga}$ alloy was prepared by a conventional arc-melting method in argon atmosphere. MCE was measured by a direct method in a calorimetric system at constant temperatures in the vicinity of MSPT. The sample for the measurement of MCE was fixed by glass wires of 10 mm in diameter glued to the sample. The change in the temperature of the sample, $\Delta T$, with the change in magnetic field, $\Delta H$, was measured by a differential thermocouple. A cooper screen was placed near the sample in order to decrease radiational losses. The magnetic field up to 26 kOe was created by an electromagnet.

The temperature dependence of $\Delta T$ at turning the magnetic field off is presented in Fig. 1. The experimental results obtained evidence that the $\Delta T$ dependence has a peak at $T \approx 340$ K. This temperature corresponds to the temperature of MSPT [1].

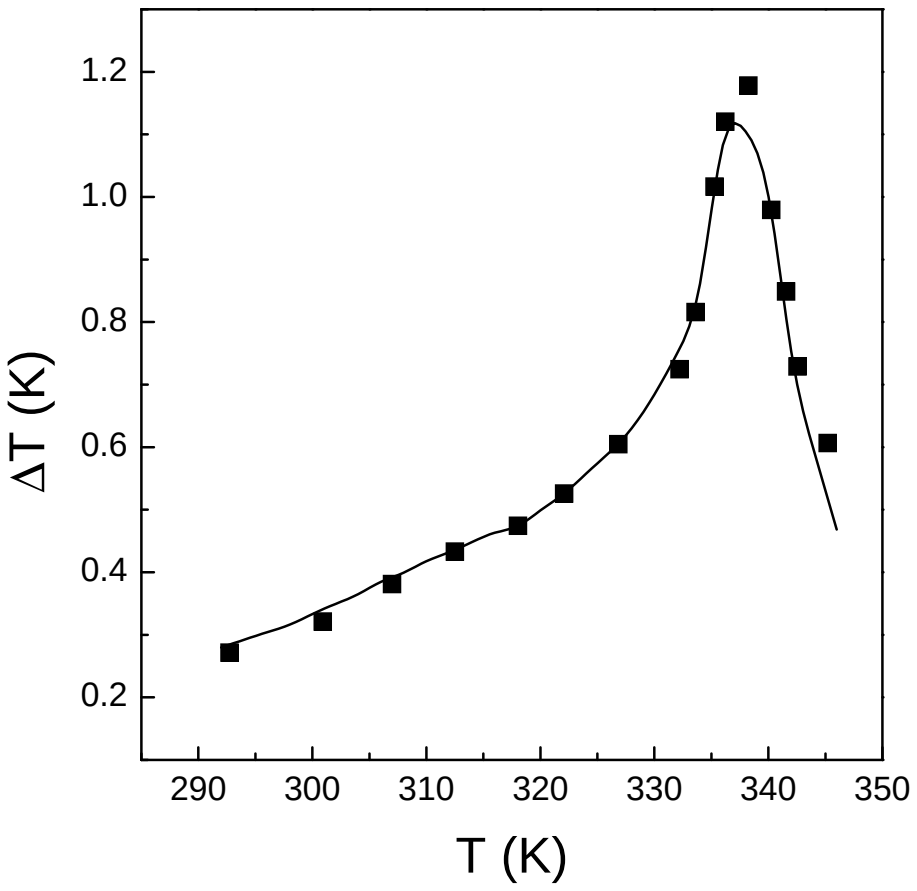

FIG. 1: Temperature dependence of sample temperature change $\Delta T$. Points are experimental data, the solid curve is theoretical one.

A statistical model is suggested for the theoretical description of the alloy properties near MSPT. The model takes into account coexistence of three types of martensitic and one type of austenitic structural domains in the vicinity of MSPT point [3,4]. Each structural domain is divided by 180° magnetic domains. It is postulated that the rate of transformation between structural domains is proportional to the net probability of transformation. This probability is expressed using the value of energetic barrier between the domains

$$P_{\alpha\beta} = \exp\Big( - \frac{\Delta V b_{\alpha\beta}}{kT} \Big) \tag{1}$$

where $\Delta V$ is the transformation volume, $b_{\alpha\beta}$ is the energetic barrier for transitions from $\alpha$ phase to $\beta$ phase ($\alpha$

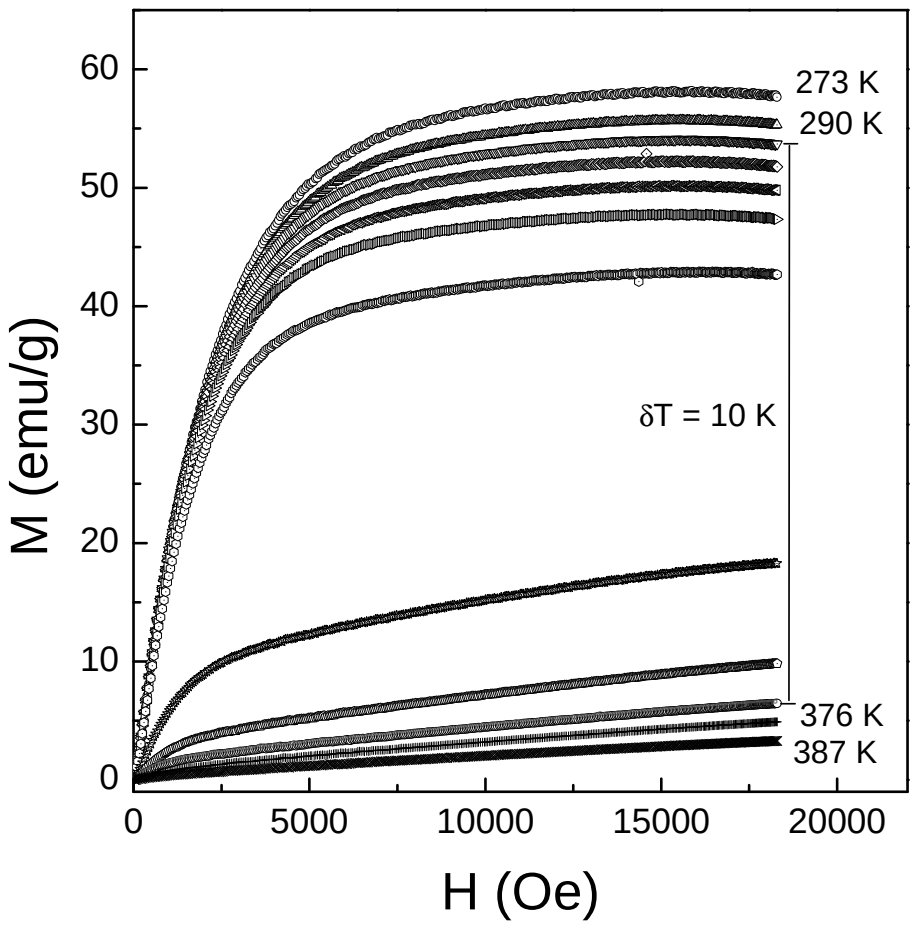

FIG. 2: Isothermal magnetization curves for $Ni_{2.19}Mn_{0.81}Ga$.

and $\beta$ are the numbers of structural domains). The magnitude of the potential barrier can be obtained as the energy at the point where Gibbs potentials of $\alpha$ phase and $\beta$ phase are equal for a fixed value of stress. Gibbs potential is $G = F - SE$, where $F$ is free energy, $S$ and $E$ are stress and strain. The free energy of the sample consists of magnetic, magnetoelastic and elastic terms. The evolution of the system depends on the energetic impacts of each phase. The rate of transformation from one phase to another is determined by

$$\dot{\xi}^{\alpha} = \sum_{\alpha}^{\beta \neq \alpha} \omega (P_{\beta\alpha}\xi^{\beta} - P_{\alpha\beta}\xi^{\alpha}), \tag{2}$$

where $\omega$ is the frequency of attempt, $\xi^{\alpha}$ is a volume fraction of $\alpha$ phase. From equation (2) we can find the volume fraction of each phase. Then the magnetization of the sample can be found as

$$M = \sum_{\alpha=1}^{4} \xi^{\alpha} M^{\alpha}, \tag{3}$$

where $M^{\alpha}$ is the magnetization of $\alpha$ phase. Using (3) we can obtain the temperature change corresponding to the change in magnetic field [5]

$$\Delta T = -\Big(\frac{T}{C_{P,H}}\Big)\Big(\frac{dM}{dT}\Big)_H \Delta H, \tag{4}$$

where $C_{P,H}$ is specific heat of the alloy.

Numerical calculation was made with the following parameters of the alloy $C_{P,H} = 25$ J/kg K, $\Delta V = 0.2 \times 10^{-25}$ m$^3$, $T_m = T_C = 340$ K, $\Delta H = 26$ kOe. The results are presented in Fig. 1 by the solid line. It is seen that for the given parameters the results of calculation are in a good agreement with the experimental results.

From Fig. 2 we can determine the magnetic entropy change $\Delta S$ at MSPT using Maxwell relation. This value is about 4.5 J/kg K at 15 kOe, which is comparable with that observed in the same magnetic field at the martensitic transition temperature in a $Ni_{2.104}Mn_{0.924}Ga_{0.972}$ composition [6].

The work was partially supported by grants RFBR-BRFBR 02-02-81030 Bel2002a, RFBR 03-02-17443, 02-02-16636a and RF Ministry of Education No E02-3.4-35.

---

[1] A.N. Vasil'ev, V.D. Buchelnikov, T. Takagi, V.V. Khovailo, and E.I. Estrin, Physics - Uspekhi 173 (2003) 577.

[2] O. Tegus, E. Brück, L. Zhang, Dagula, K.H.J. Buschow, and F.R. de Boer, Physica B 319 (2002) 174.

[3] S. Govindjee and G.J. Hall, Int. J. Sol. Struct. 37 (2000) 735.

[4] V.D. Buchelnikov and S.I. Bosko, J. Magn. Magn. Mater. 258-259 (2003) 497.

[5] S.V. Vonsovsky, *Magnetism* (Nauka, Moscow, 1971), p.402.

[6] F. Hu, B. Shen, J. Sun and G. Wu, Phys. Rev. B 64 (2001) 132412.